



# CONCRETE MIX DESIGN

DarCole Products, Inc.  
 1940 US 41 South  
 Sebree, KY 42455  
 USA (270) 826-6499

Customer:	Fc Mix
Description:	2500PSI with Air

Mix Code:	UTFCM2.5KEXT81220
Date:	8/12/2020

Air Range:	Minimum	3.0%
	Maximum	7.0%
Slump Range:	Minimum	3"
	Maximum	5"
Aggregate Ratio:	Coarse	54%
	Fine	46%

Compressive Strength:	2500 PSI
Mortar Content %:	55.6%
Paste Content %:	26.4%
Mix Suitability Factor:	22.69
Unit Weight:	142.4
Water/Cement ratio:	0.52

Material Description	Specification	Quantity (lbs)	Density	Volume
<b>Cementious</b>				
Cement	Holcim 1P Blend	423	3.000	2.26
<b>Coarse Aggregates</b>				
Coarse Aggregate 1	Kilgore 21-05014 #67 Washed Rock	1725	2.554	10.82
<b>Fine Aggregates</b>				
Fine Aggregate 1	Kilgore 22-09514 Washed Concrete Sand	1477	2.618	9.04
	Water: 26.4 gallons	219.96	1.000	3.53
	Air Content 5.0%			1.35
Total:		3845		27.00

Admixture(s)	Material Description	Specification	OZ/CWT	Density	OZ/YD
DSA 110	DarCole Synthetic Air 110	AASHTO M-154	1	1.000	4.23
DNL 785	DarCole Products DarNlok 785	AASHTO M-194 Type A	10	1.030	42.30

Reported by:	Ryan Risley-DarCole Products Inc.	Approval by:	
Date:	8/12/2020	Date:	

Disclaimer: The information in this chart is to the best of our knowledge, reliable. Users should make their own tests to determine the suitability of these for their own particular purposes. DarCole Products, Inc. makes no warranty of any kind, express or implied, including those of merchantable and fitness for purpose.




# CONCRETE MIX DESIGN

DarCole Products, Inc.  
 1940 US 41 South  
 Sebree, KY 42455  
 USA (270) 826-6499

Customer:	Fc Mix	Mix Code:	UTFCM2.5KEXT81220
Description:	2500PSI with Air	Date:	8/12/2020

Mix Analysis											
			Paste & Mortar								
			Vol	%Total	% Agg	%Mortar	%Paste				
55.6%	% Mortar										
38.7%	% Ag Retained on 3/8 Sieve										
21.6%	% Ag Passing 3/8 but Retained on #8 Sieve	+3/8	7.68	28.5%	38.7%						
64.1%	Coarseness Factor	3/8-#8	4.30	15.9%	21.6%						
39.7%	Workability (Paste + Ag < #8 Sieve)	+#8	11.98	44.4%	60.3%						
35.9%	Cement Factor Adjusted Workability	-#8	7.88	29.2%	39.7%	52.5%					
21.97	Modified Specific Surface	Mortar	15.02	55.6%							
22.69	Mix Suitability Factor	Paste	7.13	26.4%		47.5%					
Mix Suitability Factor Guidelines		Slump Range	Powder	2.26	8.4%		15.0%	31.7%			
16-20	Unstable, too Harsh	0	Air	1.35	5.0%		9.0%	18.9%			
20-22	Harsh Mixes-Heavy Vibration	0-2	Water	3.53	13.1%		23.5%	49.4%			
22-25	Hard Wearing-Slabs, Precast	2-3.5	TOTAL	27.00	100.0%	100.0%	100.0%	100.0%			
25-27	Structural Concrete	3-4	<b>Calculated for Total</b>								
26-28	Good Pumpable Concrete=Good Surface	4-5									
27-31	Pumpable, Lightweight, Flowing	>8									

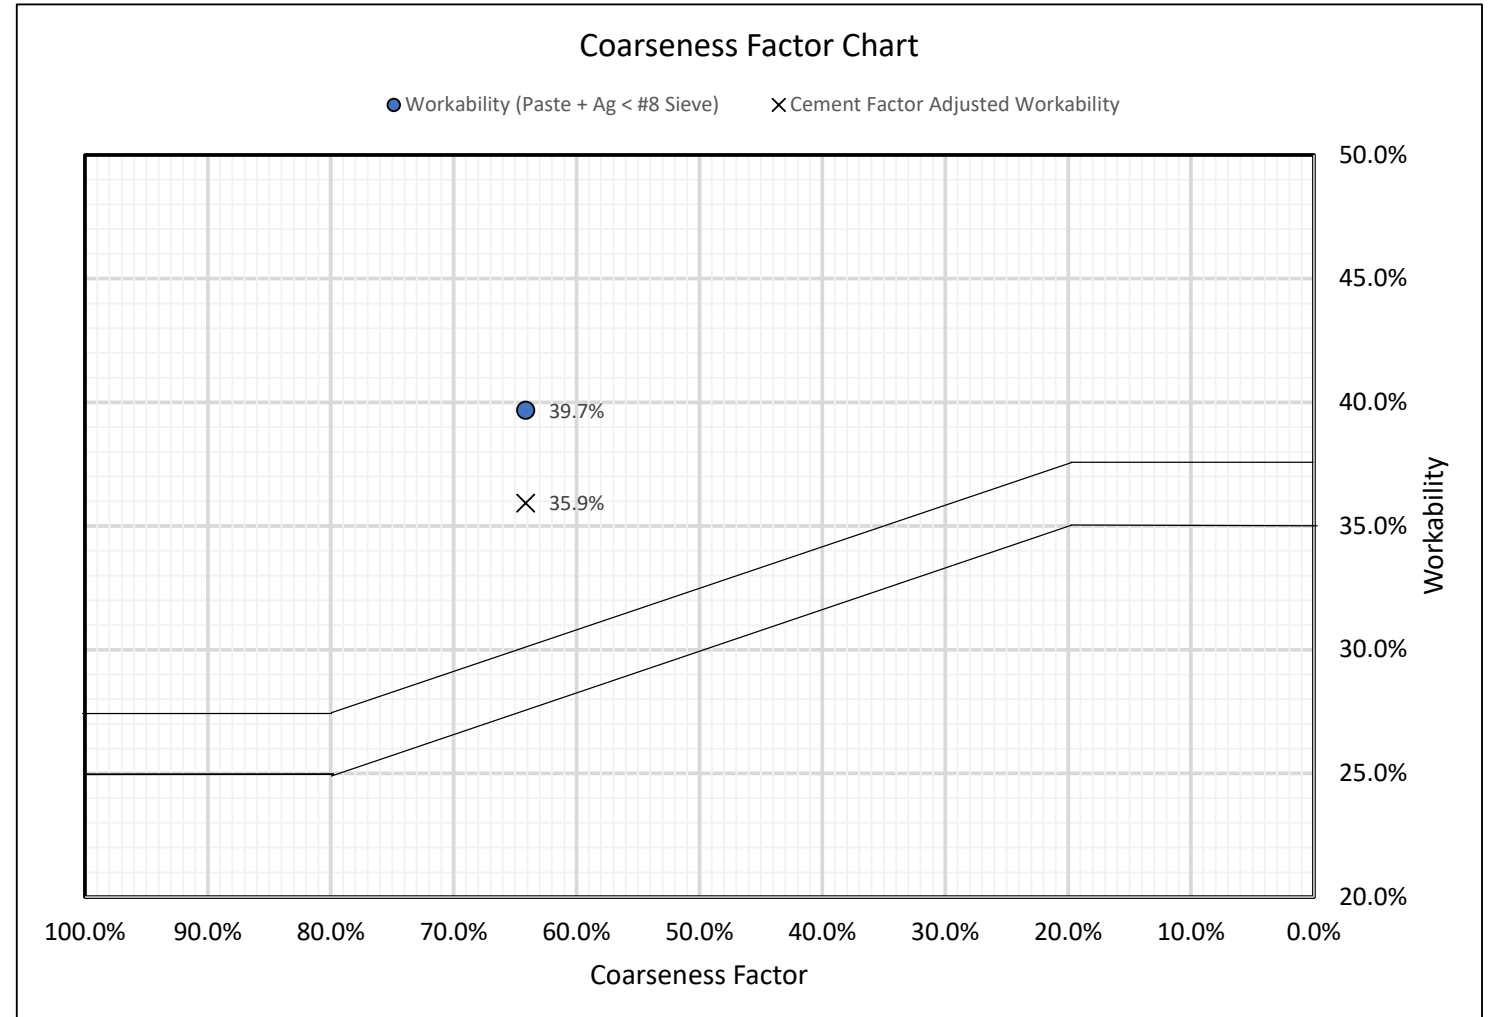



# CONCRETE MIX DESIGN

DarCole Products, Inc.  
 1940 US 41 South  
 Sebree, KY 42455  
 USA (270) 826-6499

Customer:	Fc Mix	Mix Code:	UTFCM2.5KEXT81220
Description:	2500PSI with Air	Date:	8/12/2020

## Aggregate Sieve Analysis


Sieve	Coarse Agg 1		Coarse Agg 2		Fine Agg 1		Fine Agg 2		Combined Ag		Paste+Agg	
1 1/2"	100.0%	0.0%			100.0%	0.0%			100.0%	0.0%	100.0%	0.0%
1"	100.0%	0.0%			100.0%	0.0%			100.0%	0.0%	100.0%	0.0%
3/4"	90.0%	10.0%			100.0%	0.0%			94.6%	5.4%	96.0%	4.0%
1/2"	53.0%	47.0%			100.0%	0.0%			74.4%	25.6%	81.2%	18.8%
3/8"	29.0%	71.0%			100.0%	0.0%			61.3%	38.7%	71.5%	28.5%
# 4	4.0%	96.0%			100.0%	0.0%			47.7%	52.3%	61.5%	38.5%
# 8	1.0%	99.0%			86.0%	14.0%			39.7%	60.3%	55.6%	44.4%
# 16	1.0%	99.0%			53.0%	47.0%			24.7%	75.3%	44.6%	55.4%
# 30	1.0%	99.0%			33.0%	67.0%			15.6%	84.4%	37.9%	62.1%
# 50	1.0%	99.0%			21.0%	79.0%			10.1%	89.9%	33.9%	66.1%
# 100	1.0%	99.0%			8.0%	92.0%			4.2%	95.8%	29.5%	70.5%
# 200	0.5%	99.5%			2.2%	97.8%			1.3%	98.7%	18.5%	81.5%
# 325	0.0%	100.0%			0.0%	100.0%			0.0%	100.0%		
% Agg	54.5%				45.5%							

Percent Passing
Percent Retained

	Fine Agg 1	Fine Agg 2
F.M.	2.99	

F.M. Guidelines	
Fine Sand	2.2-2.6
Medium Sand	2.6-2.9
Coarse Sand	2.9-3.2

Coarse Aggregate 1      Kilgore 21-05014 #67 Washed Rock  
 Coarse Aggregate 2  
 Fine Aggregate 1      Kilgore 22-09514 Washed Concrete Sand  
 Fine Aggregate 2

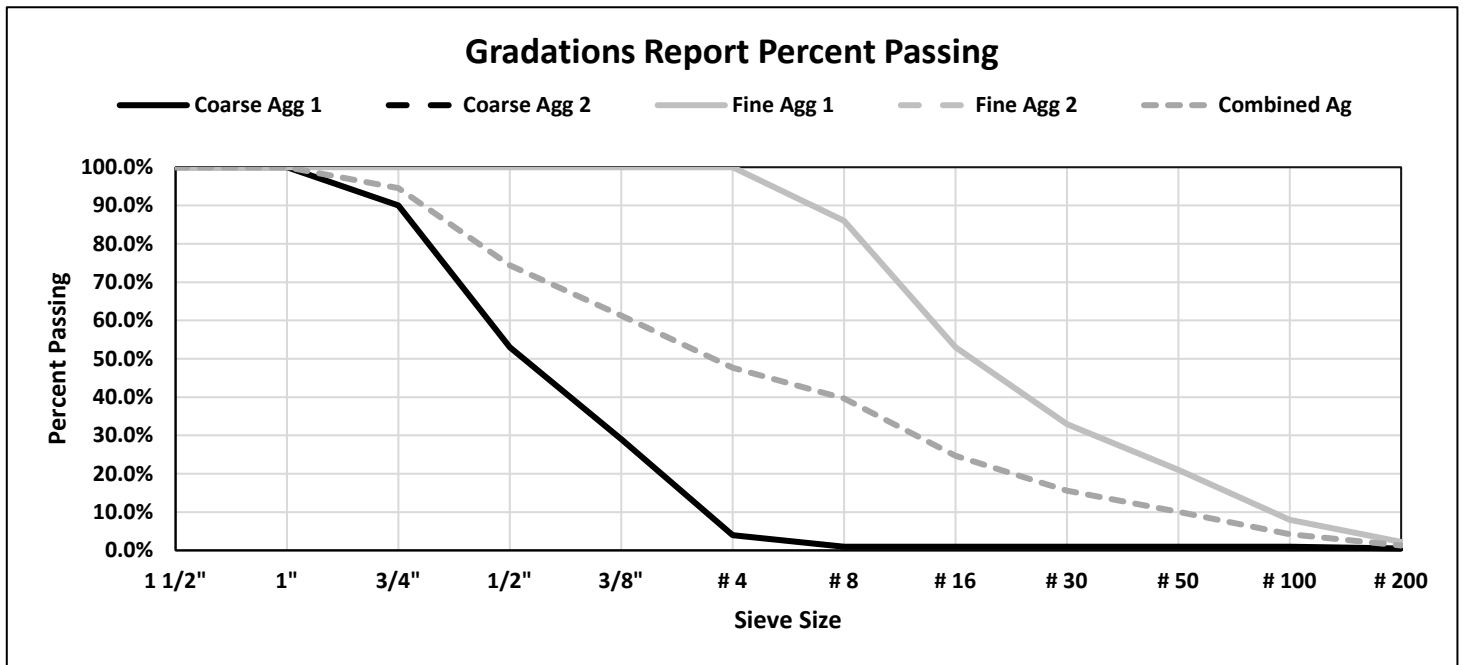



# CONCRETE MIX DESIGN

DarCole Products, Inc.  
 1940 US 41 South  
 Sebree, KY 42455  
 USA (270) 826-6499

Customer:	Fc Mix	Mix Code:	UTFCM2.5KEXT81220
Description:	2500PSI with Air	Date:	8/12/2020

Individual Percent Retained						
Sieve	Coarse Agg 1	Coarse Agg 2	Fine Agg 1	Fine Agg 2	Combined Ag	Paste + Ag
1 1/2"	0.0%		0.0%		0.0%	0.0%
1"	0.0%		0.0%		0.0%	0.0%
3/4"	10.0%		0.0%		5.4%	4.0%
1/2"	37.0%		0.0%		20.2%	14.8%
3/8"	24.0%		0.0%		13.1%	9.6%
# 4	25.0%		0.0%		13.6%	10.0%
# 8	3.0%		14.0%		8.0%	5.9%
# 16	0.0%		33.0%		15.0%	11.1%
# 30	0.0%		20.0%		9.1%	6.7%
# 50	0.0%		12.0%		5.5%	4.0%
# 100	0.0%		13.0%		5.9%	4.4%
# 200	0.5%		5.8%		2.9%	11.0%
% Agg	54.5%		45.5%			

Coarse Aggregate 1                      Kilgore 21-05014 #67 Washed Rock

Coarse Aggregate 2

Fine Aggregate 1                      Kilgore 22-09514 Washed Concrete Sand

Fine Aggregate 2

